


Laminate Stretch Test Report


Style : RDFT5000 act. weight : 226 g/m²
 Lot-No. : 66066 act. weight : 5,28 smoz

Legende	warp 0° Nr	condition	10 lbf	25 lbf	50 lbf	100 lbf	200 lbf	1% lbf
	1.1	lab	0,7	1,4	2,3	3,8	6,6	511,4
	1.2	flutter	0,7	1,3	2,1	3,7	6,6	492,1

Legende	fill 90° Nr	condition	10 lbf	25 lbf	50 lbf	100 lbf	200 lbf	1% lbf
	2.1	lab	1,1	2,5	4,5	8,6	17,1	186,3
	2.2	flutter	1,1	2,7	5,1	9,8	20,0	160,8

Legende	bias 45° Nr	condition	10 lbf	25 lbf	50 lbf	100 lbf	200 lbf	1% lbf
	3.1	lab	1,5	3,1	5,3	9,7	19,6	166,2
	3.2	flutter	1,1	2,7	5,0	9,5	20,2	163,6

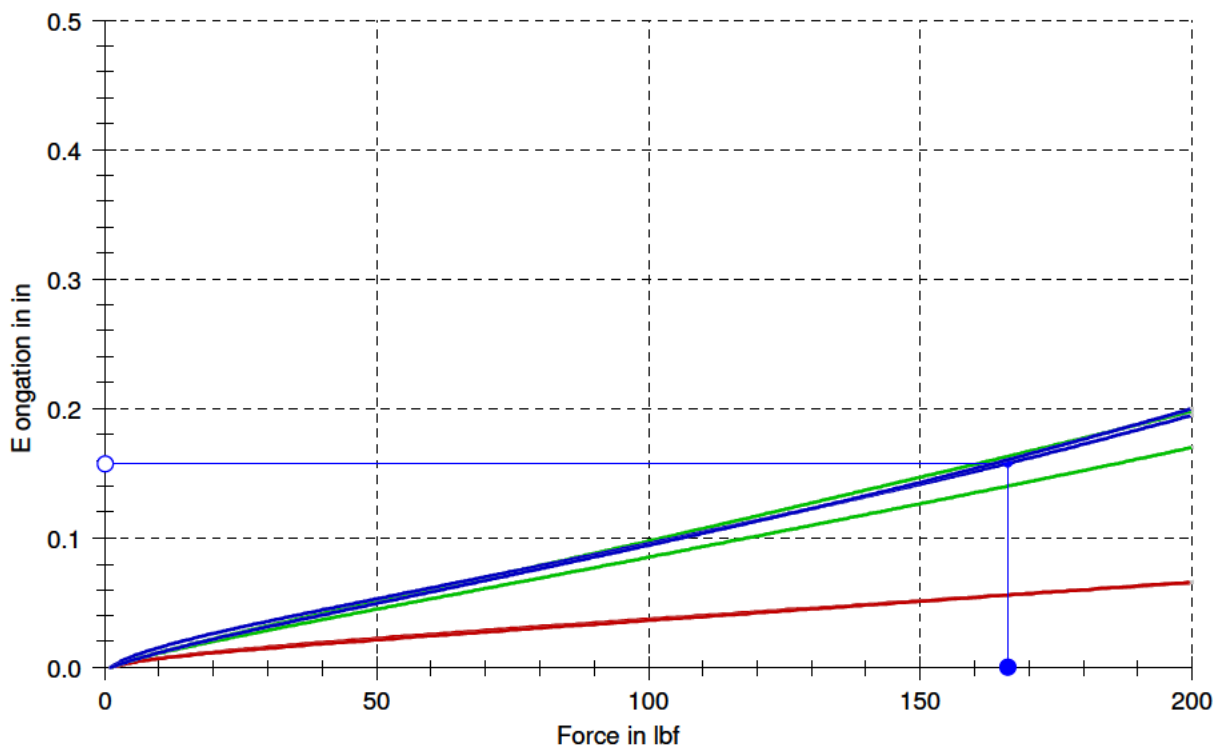

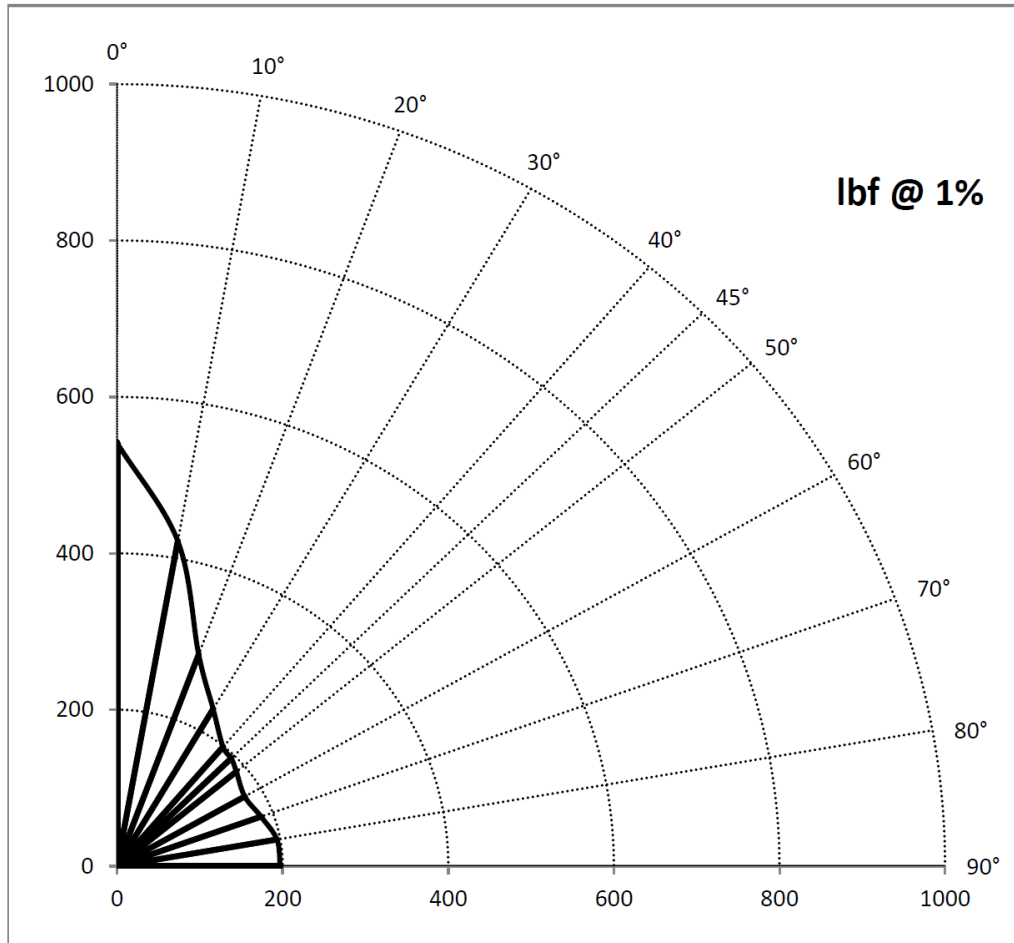

Style: RDFT5000 radial

Lot: 66066

Weight: 212 g/m², 5.0 smoz

Yarn: Aramid

0° 14400 dpi

90° 3600 dpi

± 45° 3600 dpi


Laminate Stretch Test Report


Style : RDFT5001 act. weight : 201 g/m²
 Lot-No. : 65942 act. weight : 4,70 smoz

Legende	warp 0° Nr	condition	10 lbf	25 lbf	50 lbf	100 lbf	200 lbf	1% lbf
	1.1	lab	0,4	1,1	2,0	4,0	8,0	391,5
	1.2	flutter	0,5	1,1	2,0	3,9	7,8	408,8

Legende	fill 90° Nr	condition	10 lbf	25 lbf	50 lbf	100 lbf	200 lbf	1% lbf
	2.1	lab	1,1	2,8	5,3	10,0	20,3	158,7
	2.2	flutter	1,2	2,7	4,9	9,2	18,0	176,8

Legende	bias 45° Nr	condition	10 lbf	25 lbf	50 lbf	100 lbf	200 lbf	1% lbf
	3.1	lab	0,9	2,1	4,2	8,3	18,5	177,6
	3.2	flutter	0,7	1,9	3,8	7,7	17,3	187,4

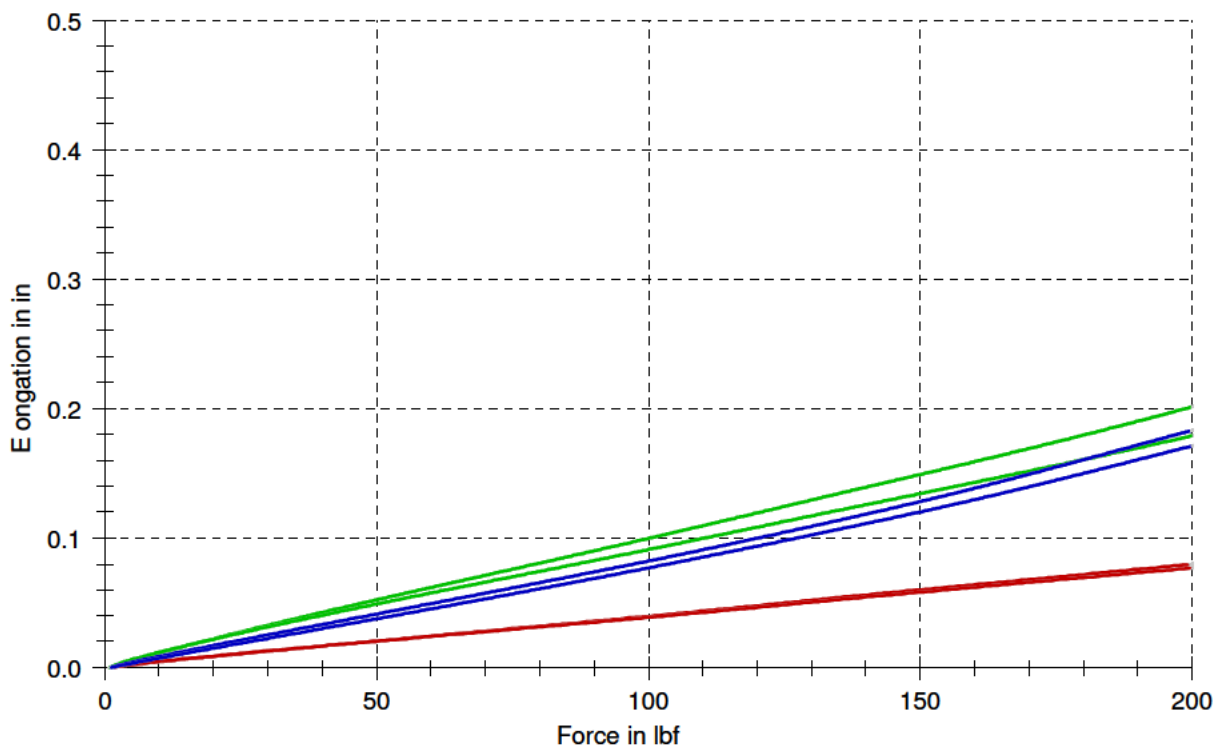

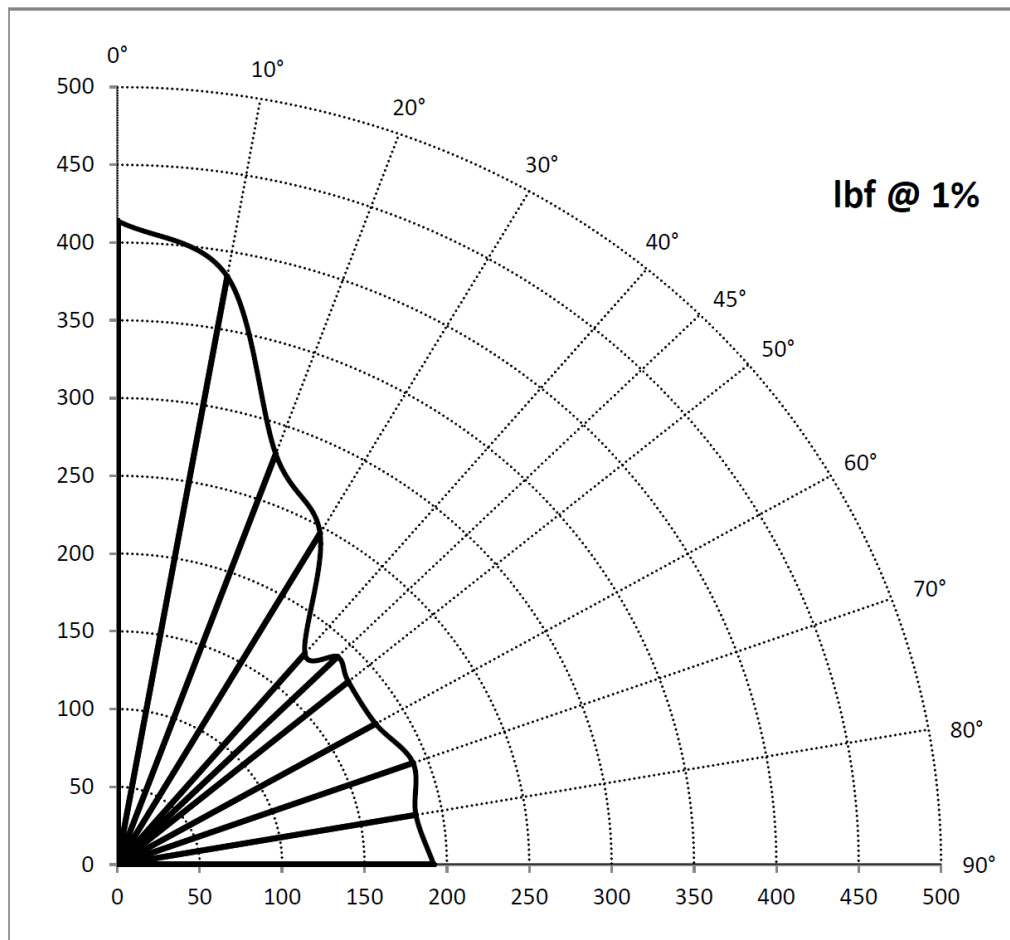

Style: RDFT5001 radial

Lot: 65942

Weight: 194 g/m², 4.5 smoz

Yarn: Aramid

0° 9600 dpi

90° 3600 dpi

± 45° 3600 dpi

Laminate Stretch Test Report

05.08.22


Style : RDFT 5003


act. weight : 261 g/m²
act . weight : 6,10 smoz

Legende	warp 0° Nr	condition	10 lbf	25 lbf	50 lbf	100 lbf	200 lbf	1% lbf
	1.1	lab	0,5	0,9	1,5	2,7	4,9	691,1
	1.2	flutter	0,6	1,2	2,0	3,2	5,5	647,2

Legende	fill 90° Nr	condition	10 lbf	25 lbf	50 lbf	100 lbf	200 lbf	1% lbf
	2.1	lab	1,2	2,8	5,1	9,7	19,0	167,3
	2.2	flutter	1,8	3,6	6,2	11,1	21,6	148,4

Legende	bias 45° Nr	condition	10 lbf	25 lbf	50 lbf	100 lbf	200 lbf	1% lbf
	3.1	lab	1,2	2,6	4,7	9,0	19,1	172,2
	3.2	flutter	1,6	3,1	5,2	9,3	18,4	174,9

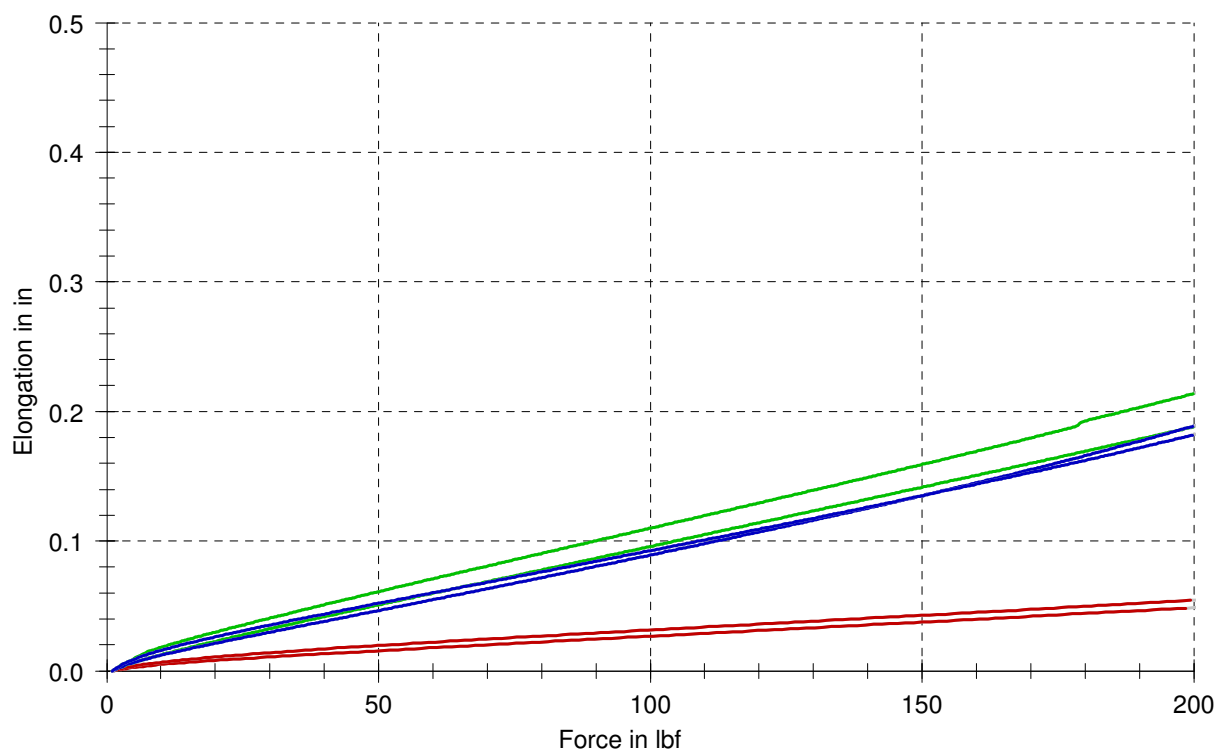

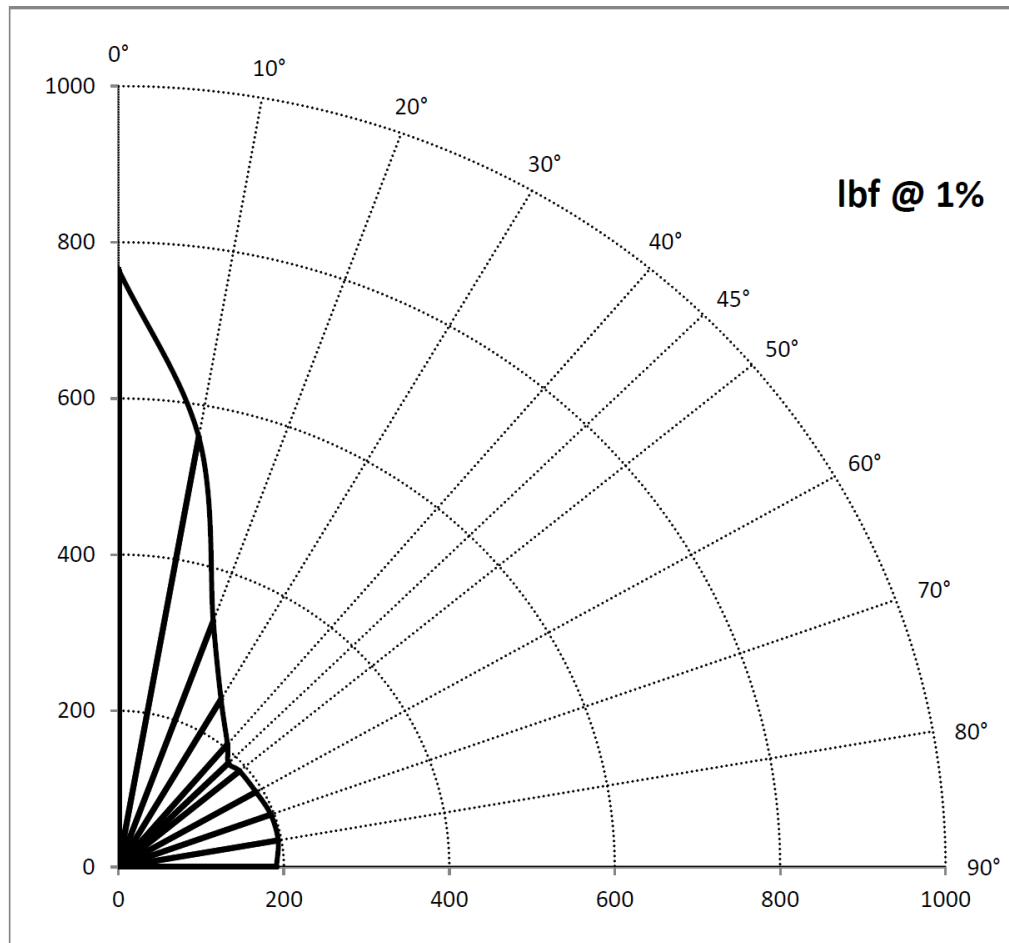

Style: RDFT5003 radial

Lot: 66249

Weight: 263 g/m², 6.1 smoz

Yarn: Aramid

0° 19200 dpi

90° 3600 dpi

± 45° 3600 dpi


Laminate Stretch Test Report


Style : RDFT 5004 act. weight : 144 g/m²
 Lot-No. : 66283 act. weight : 3,36 smoz

Legende	warp 0° Nr	condition	10 lbf	25 lbf	50 lbf	100 lbf	200 lbf	1% lbf
	1.1	lab	0,9	2,2	4,0	7,5	14,4	221,9
	1.2	flutter	1,4	2,8	4,8	8,6	16,3	195,3

Legende	fill 90° Nr	condition	10 lbf	25 lbf	50 lbf	100 lbf	200 lbf	1% lbf
	2.1	lab	1,3	3,3	6,4	12,7	26,7	124,9
	2.2	flutter	1,9	3,8	7,0	13,2	27,9	121,0

Legende	bias 45° Nr	condition	10 lbf	25 lbf	50 lbf	100 lbf	200 lbf	1% lbf
	3.1	lab	1,5	3,4	6,2	11,8	25,1	134,3
	3.2	flutter	2,0	4,2	7,2	13,1	27,4	122,2

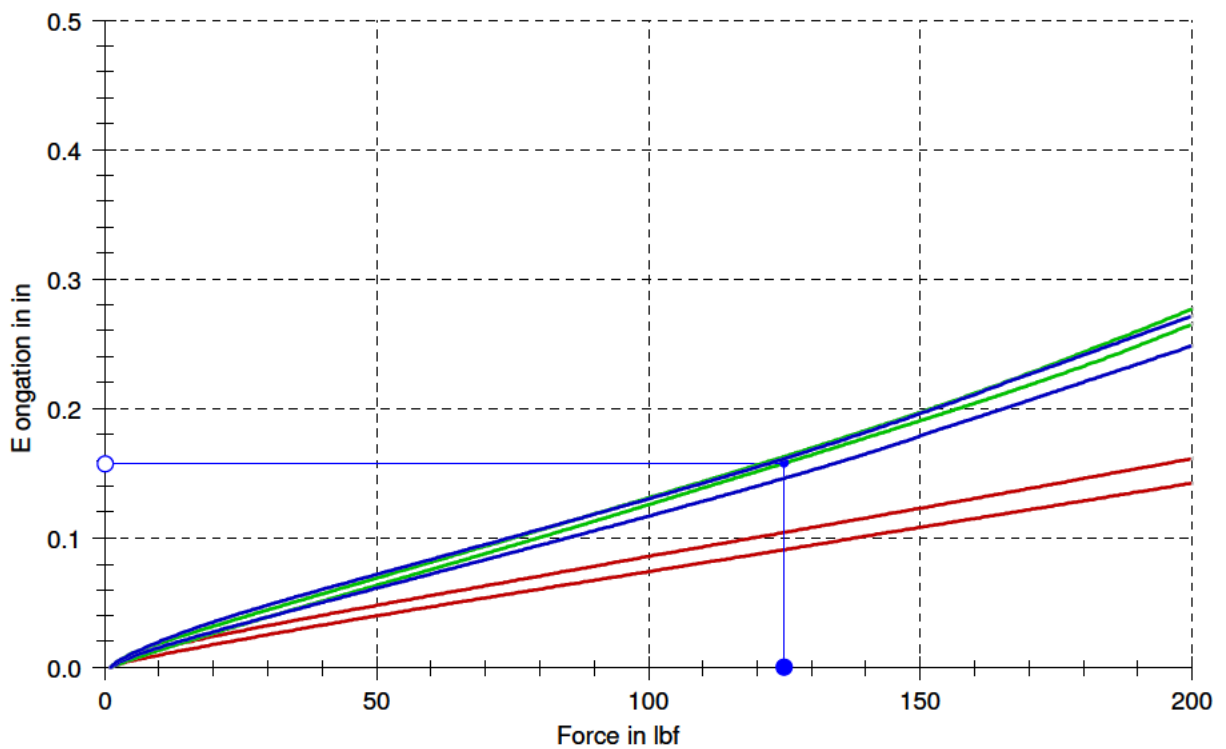

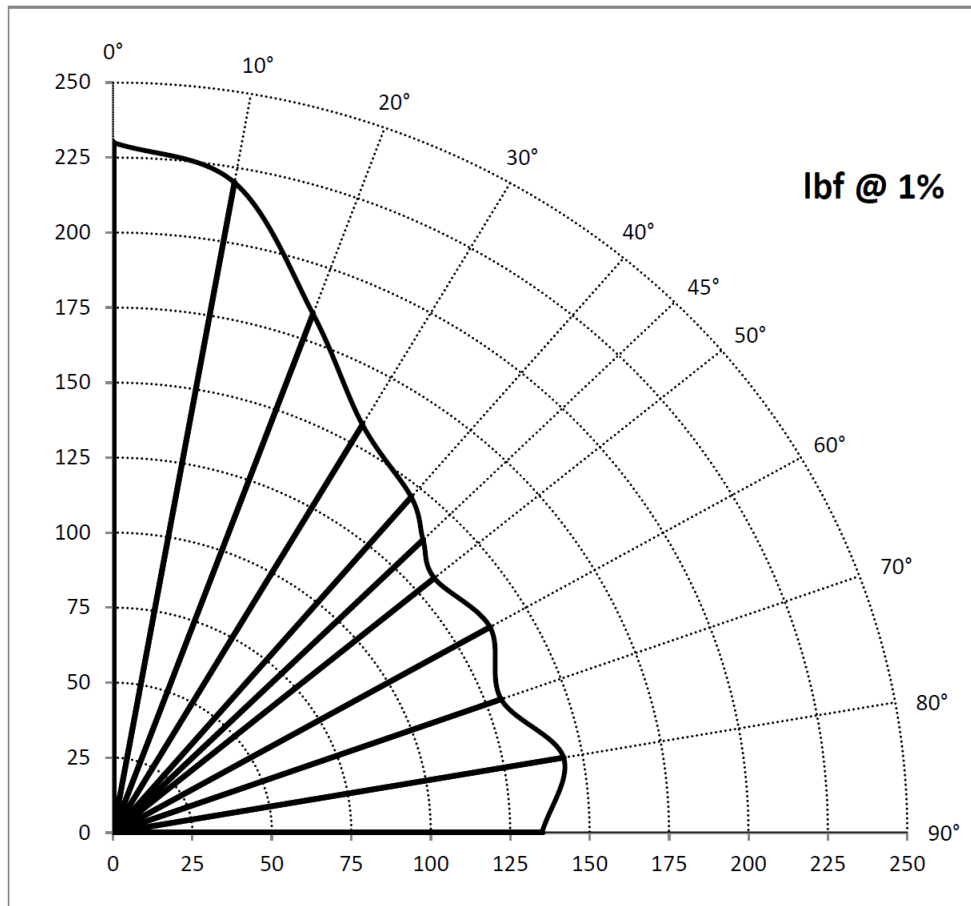

Style: RDFT5004 radial

Lot: 66283

Weight: 142 g/m², 3.3 smoz

Yarn: Aramid black

0° 5000 dpi

90° 2500 dpi

± 45° 2500 dpi

Laminate Stretch Test Report

Style : RDFT 5005


act. weight : 150 g/m²


act. weight : 3,50 smoz

Legende	warp 0° Nr	condition	10 lbf	25 lbf	50 lbf	100 lbf	200 lbf	1% lbf
	1.1	lab	1,2	2,4	3,9	6,8	12,6	257,2
	1.2	flutter	1,1	2,2	3,9	7,0	13,1	245,7

Legende	fill 90° Nr	condition	10 lbf	25 lbf	50 lbf	100 lbf	200 lbf	1% lbf
	2.1	lab	1,4	3,2	6,0	11,7	23,6	136,6
	2.2	flutter	2,4	4,6	7,9	14,2	28,2	112,7

Legende	bias 45° Nr	condition	10 lbf	25 lbf	50 lbf	100 lbf	200 lbf	1% lbf
	3.1	lab	1,2	3,2	6,4	12,9	29,2	121,1
	3.2	flutter	1,9	4,0	7,2	13,8	30,9	114,8

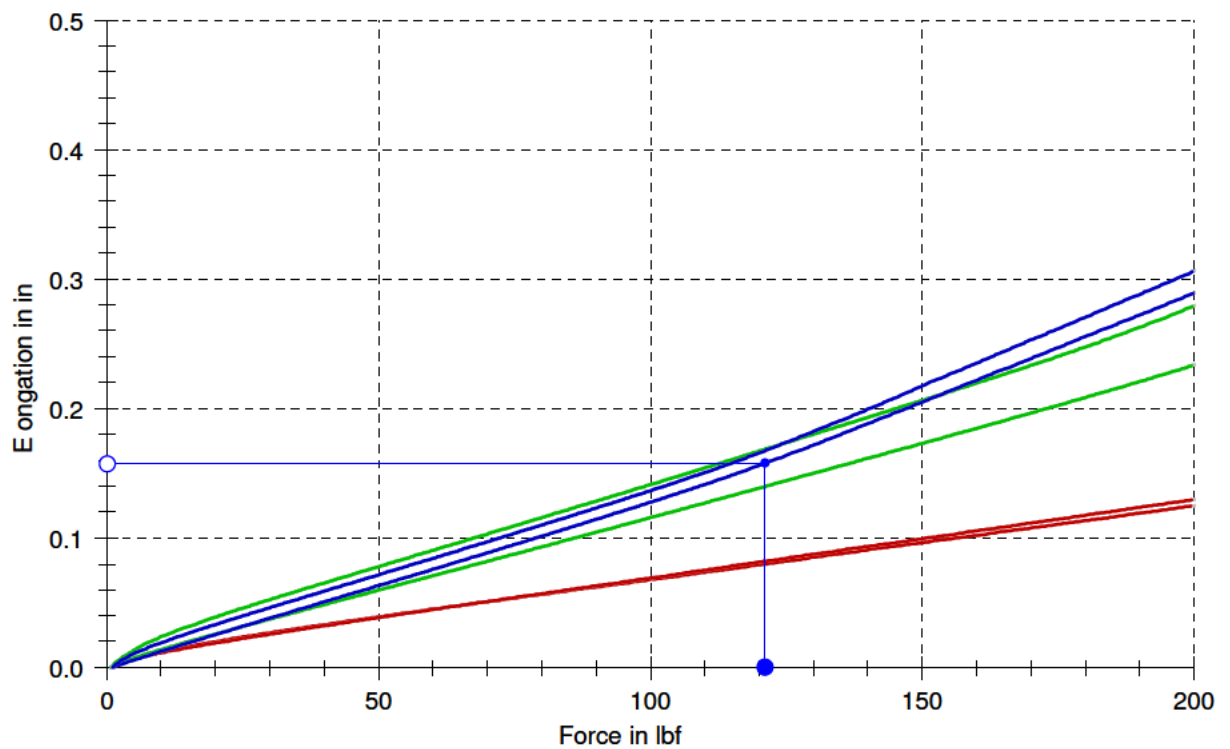

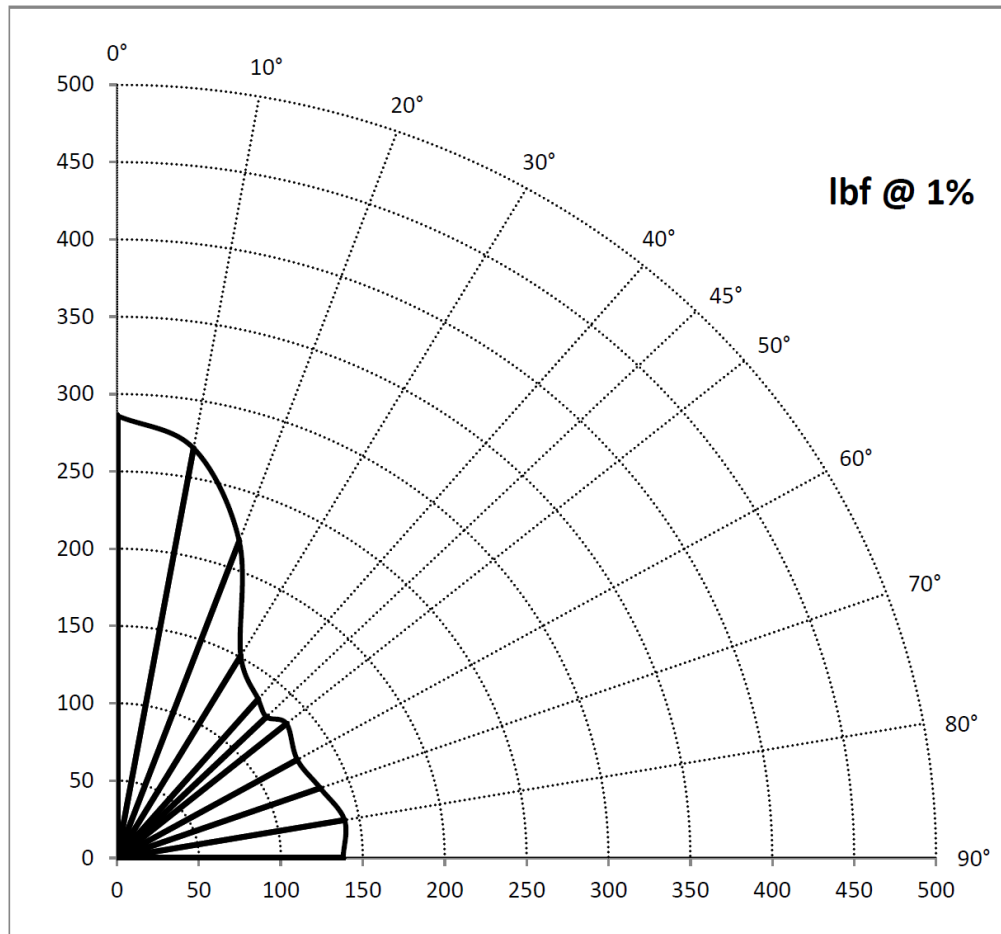

Style: RDFT5005 radial

Lot: 66284

Weight: 153 g/m², 3.6 smoz

Yarn: Aramid black

0° 7100 dpi

90° 2500 dpi

± 45° 2500 dpi